

Suprasil® CG

Suprasil® CG is a high purity synthetic fused silica material manufactured by flame hydrolysis. It combines excellent physical properties with very good optical characteristics and excellent transmission from the deep UV to the near IR.

Technical features

- Low Bubble and Inclusion content
 - ▶ Ø 140 mm bubble class O, occasionally isolated bubbles
 - ▶ Ø 320 mm bubble class O, 1/ 1 * 0.16
 - ▶ Ø 650 mm bubble class O, 1/ 1 * 0.16
- High Purity
- UV-Transmission (typical)
 - ▶ k_{200} : $3.5 \cdot 10^{-3}$ / cm
- Standard Homogeneity in functional direction
 - ▶ not specified
 - ▶ Striae: MIL G 174 B Grade A
- Stress Induced Birefringence in functional direction
 - ▶ SIB ≤ 20 nm / cm
- Well established production processes




Refractive index and dispersion

n_c	= 1.45637 at 656.3 nm
n_d	= 1.45846 at 587.6 nm
n_F	= 1.46313 at 486.1 nm
n_g	= 1.46669 at 435.8 nm
n	= 1.50833 at 248.4 nm

At 20°C, 1 bar atmospheric pressure
Accuracy: $\pm 3 \cdot 10^{-5}$

Transmission spectrum including reflection losses

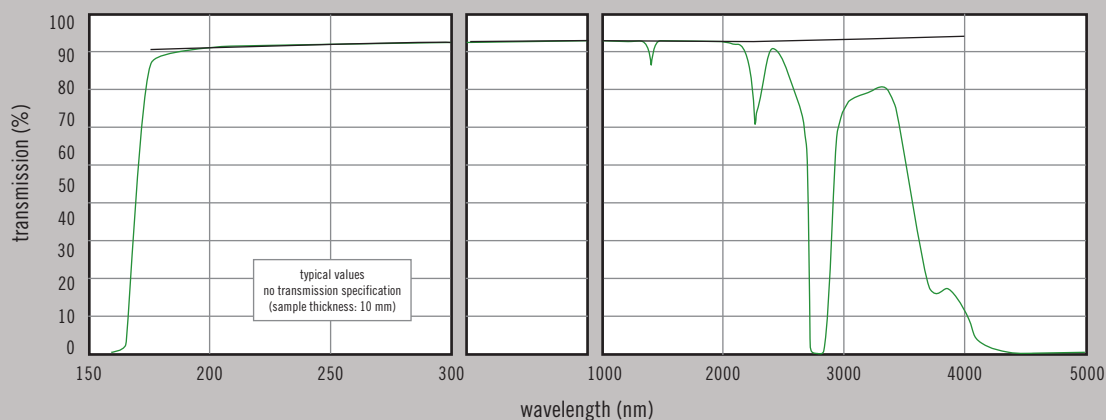

Geometry available today

Diameter Ø



Ø 650 mm



Ø 320 mm



Ø 140 mm

Minimum order length

Ø 140 mm (± 10 mm)	200 mm or a multiple thereof
Ø 320 mm (± 15 mm)	100 mm or a multiple thereof
Ø 650 mm (± 5 mm)	~ 200 mm

Typical chemical impurities in weight ppb

	AL	Ca	K	Na	Mg	Li	Cu	Fe	Ni	Cr	Mn	Ti	OH (ppm)
Suprasil® CG	≤10	≤15	≤10	≤10	≤5	≤1	≤3	≤5	≤1	≤1	≤2	≤5	400 – 1000

Mechanical Properties

Density (g/cm ³)	2.2
Mohs hardness	5.5 ... 6.5
Micro hardness (N/mm ²)	8600 ... 9800
Knoop hardness (N/mm ²)	5800 ... 6200
Modulus of elasticity at 20°C (N/mm ²)	7.0 · 10 ⁴
Modulus of torsion (N/mm ²)	3.0 · 10 ⁴
Poisson's ratio	0.17
Compressive strength (approx.) (N/mm ²)	1150
Tensile strength (approx.) (N/mm ²)	50
Bending strength (approx.) (N/mm ²)	67
Torsional strength (approx.) (N/mm ²)	30
Sound velocity (m/s)	5720

Mean specific heat (J/kg · K)

0 ... 100°C	772
0 ... 500°C	964
0 ... 900°C	1052

Heat conductivity (W/m · K)

20°C	1.38
100°C	1.46
200°C	1.55
300°C	1.67
400°C	1.84
950°C	2.68

Thermal Properties

Softening temperature (°C)	1600
Annealing temperature (°C)	1120
Strain temperature (°C)	1025
Max. working temperature continuous (°C)	950
short-therm (°C)	1200

Mean expansion coefficient (K⁻¹)

-50 ... 0°C	2.7 · 10 ⁻⁷
0 ... 100°C	5.1 · 10 ⁻⁷
0 ... 200°C	5.8 · 10 ⁻⁷
0 ... 300°C	5.9 · 10 ⁻⁷
0 ... 600°C	5.4 · 10 ⁻⁷
0 ... 900°C	4.8 · 10 ⁻⁷

Germany

Heraeus Quarzglas GmbH & Co. KG

Heraeus Conamic

Optics

Quarzstraße 8

63450 Hanau

Phone +49 (6181) 35-62 85

Fax +49 (6181) 35-62 70

conamic.optics.eu@heraeus.com

USA

Heraeus Quartz North America LLC

Heraeus Conamic

Optics

100 Heraeus Blvd.

Buford, GA 30518

Phone +1 (678) 714-4350

Fax +1 (678) 714-4355

conamic.optics.us@heraeus.com

UK

Heraeus Conamic UK Ltd.

Neptune Road, Wallsend

Tyne & Wear NE28 6DD

United Kingdom

Phone +44 (191) 259 8454

Fax +44 (191) 263 8040

conamic.optics.uk@heraeus.com

China

Heraeus (China) Investment Co., Ltd.

Heraeus Conamic

Building 5,

No. 406 Guilin Road, Xuhui District,

Shanghai 200233

Phone +86 (21) 3357 5175

Fax +86 (21) 3357 5230

conamic.optics.cn@heraeus.com