


## Spectrosil® 2000

Spectrosil® synthetic fused silica is manufactured using a patented, environmentally friendly process resulting in a glass of exceptional purity and excellent visual quality. It is a very homogeneous synthetic fused silica glass for deep UV optical applications.

Spectrosil® 2000 is chlorine-free, free of bubbles and inclusions and due to its ultra-high purity, has exceptional optical transmission in the deep ultraviolet and visible, with a useful range from below 180 nm through to 2000 nm.

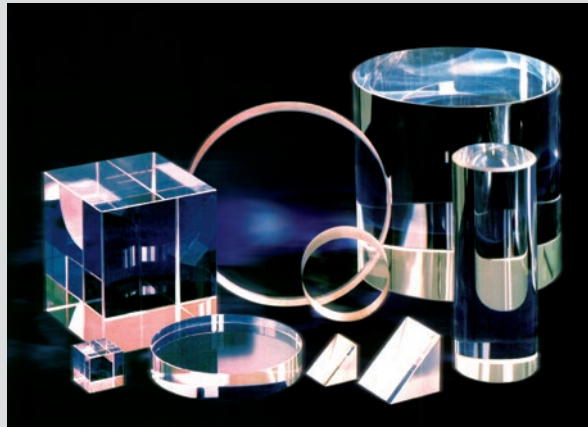

Spectrosil® Grade	2000
■ <b>Refractive Index Homogeneity</b> <sup>1)</sup>	≤ 10 ppm achievable (must be specified if needed)
■ <b>Striae</b> ISO 10110-4	Class 5 in Functional Direction
■ <b>Birefringence / Residual Strain</b> <sup>1)</sup> (Typical values)	≤ 5 nm/cm
■ <b>Bubbles</b>	
Bubble class (DIN 58927)	0
Maximum number of inclusions <sup>2)</sup>	0
■ <b>Fluorescence</b> <sup>3)</sup> (254 nm excitations)	Free

1) Stress induced birefringence and optical homogeneity are valid for 80% of the diameter of an ingot or for 90% diameter of a machined component.


2) Bubbles and Inclusions with  $\phi \leq 80 \mu\text{m}$  are not counted. Inclusions free down to  $10 \mu\text{m}$  upon request.

3) Excitation by Hg-Lamp @  $\lambda = 254 \text{ nm}$  and UQ 5-filter; Lamp-power: 8W; Detection: adapted eye

Transmission – Typical Internal Transmission (10 mm path length)		
	$\lambda = 193.4 \text{ nm}$	$\lambda = 248 \text{ nm}$
Spectrosil® 2000	> 98.5 %	> 99.5 %

## Typical Transmission Spectrum

Sample thickness: 10 mm

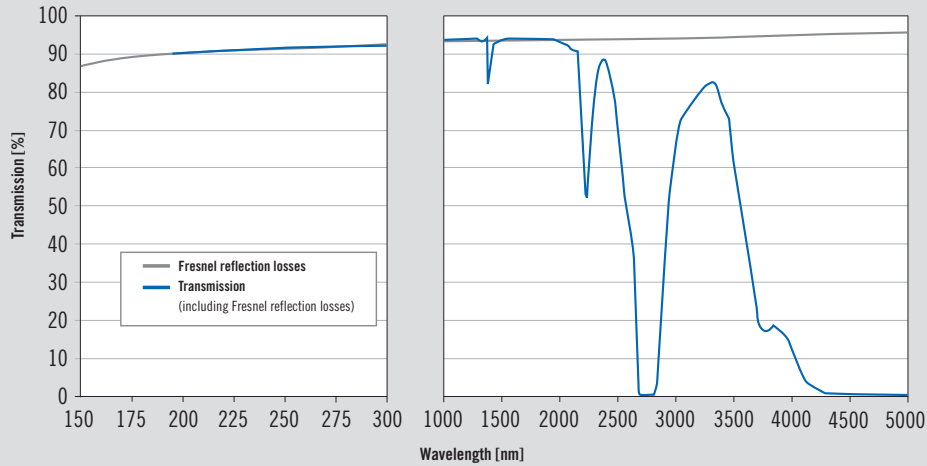

## Typical Chemical Analysis

Typical trace elements	in ppb	Al	Ca	Cr	Cu	Fe	K	Li	Mg	Na	Ti	V	in ppm	OH
Spectrosil® 2000		< 10	< 15	< 1	< 3	< 5	< 10	< 1	< 5	< 10	< 5	< 5		< 1350
		(below limits of detection)												

## Technical Properties

### Other Properties

Abbe number:	67.8
Density:	2.2 g/cm <sup>3</sup>
Hardness: (Mohs scale)	5.5 ... 6.5

### Thermal Properties

Strain temperature*:	1025 °C
Annealing temperature*:	1120 °C
Softening temperature*:	1600 °C
Coefficient of thermal expansion: (Average, K <sup>-1</sup> 0 ... 600 °C)	0.54 x 10 <sup>-6</sup>

\*Note that these values may vary, depending on the thermal history of the glass.

Germany

**Heraeus Quarzglas  
GmbH & Co. KG**

Optics  
Quarzstraße 8  
63450 Hanau  
Phone +49 (6181) 35-62 85  
Fax +49 (6181) 35-62 70  
sales.hqs.optics.de@heraeus.com

[www.optics.heraeus-quarzglas.com](http://www.optics.heraeus-quarzglas.com)

USA

**Heraeus Quartz  
North America LLC**

Optics  
100 Heraeus Blvd.  
Buford, GA 30518  
Phone +1 (678) 714-4350  
Fax +1 (678) 714-4355  
sales.hqs.optics.us@heraeus.com

UK

**Heraeus Quartz  
UK Ltd.**

Neptune Road, Wallsend  
Tyne & Wear NE28 6DD  
United Kingdom  
Phone +44 (191) 259 8454  
Fax +44 (191) 263 8040  
sales.hqs.optics.uk@heraeus.com

China

**Heraeus (China)  
Investment Co., Ltd.**

Building 5,  
No. 406 Guilin Road, Xuhui District,  
Shanghai 200233  
Phone +86 (21) 3357 5173  
Fax +86 (21) 3357 5230  
sales.hqs.optics.cn@heraeus.com